

TECHNICAL SPECIFICATION

ISO/TS
29584

First edition
2012-10-15

Glass in building — Pendulum impact testing and classification of safety glass for use in buildings

Verre dans la construction — Essai d'impact au pendule et classification du verre de sécurité utilisé dans les bâtiments

STANDARDSISO.COM : Click to view the full PDF of ISO/TS 29584:2012



Reference number
ISO/TS 29584:2012(E)

© ISO 2012



COPYRIGHT PROTECTED DOCUMENT

© ISO 2012

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

| | Page |
|---|------|
| Foreword | iv |
| Introduction | v |
| 1 Scope | 1 |
| 2 Normative references | 1 |
| 3 Terms and definitions | 2 |
| 4 Principle | 3 |
| 5 Test requirements | 3 |
| 6 Test method | 3 |
| 6.1 Test apparatus | 3 |
| 6.2 Calibration of test apparatus | 12 |
| 6.3 Test pieces | 12 |
| 6.4 Impact test procedure | 12 |
| 7 Classification | 13 |
| 7.1 General | 13 |
| 7.2 Drop height class | 14 |
| 7.3 Mode of breakage | 14 |
| 7.4 Performance classification | 14 |
| 8 Test report | 15 |
| Annex A (normative) Method of fabrication of the shot bag impactor | 17 |
| Annex B (normative) Calibration of the test rig | 23 |
| Annex C (normative) Sphere penetration test | 29 |
| Annex D (informative) Example of a test rig | 31 |
| Annex E (informative) Terms and definitions of glass types | 36 |
| Annex F (informative) Example of release mechanism | 38 |
| Bibliography | 43 |

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

In other circumstances, particularly when there is an urgent market requirement for such documents, a technical committee may decide to publish other types of document:

- an ISO Publicly Available Specification (ISO/PAS) represents an agreement between technical experts in an ISO working group and is accepted for publication if it is approved by more than 50 % of the members of the parent committee casting a vote;
- an ISO Technical Specification (ISO/TS) represents an agreement between the members of a technical committee and is accepted for publication if it is approved by 2/3 of the members of the committee casting a vote.

An ISO/PAS or ISO/TS is reviewed after three years in order to decide whether it will be confirmed for a further three years, revised to become an International Standard, or withdrawn. If the ISO/PAS or ISO/TS is confirmed, it is reviewed again after a further three years, at which time it must either be transformed into an International Standard or be withdrawn.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO/TS 29584 was prepared by Technical Committee ISO/TC 160, *Glass in building*, Subcommittee SC 2, *Use considerations*.

Introduction

This Technical Specification has been prepared as a means of detailing the differences and similarities in pendulum impact tests for the classification of safety glass.

The traditional impactor has been a lead shot-filled leather bag. This has been found to suffer from ageing or shape change and variability in the energy transfer into the test piece if not properly maintained. It has been found that there can be wide variation in the supporting frame or sub-frame.

During their work, CEN/TC 129, *Glass in building; WG 13, Safety test methods*; examined some of the problems associated with the lead shot-filled leather bag impactor and the supporting frame. CEN/TC 129/WG 13 prepared EN 12600^[5], that uses an impactor consisting of steel masses and two tyres.

The primary objectives in developing the new impactor for the evaluation of safety glass can be summarized as follows:

- a) elimination of the differences between:
 - 1) taped and untaped lead shot bags;
 - 2) lead shot bags and bags filled with sand or glass beads;
- b) ageing of lead shot bag;
- c) elimination of the use of lead shot;
- d) harmonization of national impact test methods.

STANDARDSISO.COM : Click to view the full PDF of ISO/TS 29584:2012

Glass in building — Pendulum impact testing and classification of safety glass for use in buildings

1 Scope

This Technical Specification examines test methods currently employed to determine the pendulum impact performance of safety glass. Use of the methodologies in this Technical Specification improves the reproducibility of test results and gives a common basis of classification. The aim is for the performance of glass products manufactured and tested in various countries to be better understood and accepted.

This Technical Specification evaluates, by means of soft body impactors, safe breakage characteristics of glazing products intended to reduce cutting and piercing injuries to persons through accidental impact.

This Technical Specification defines two types of soft body impactor. The traditional shot bag impactor is detailed both in terms of manufacture and maintenance in an attempt to overcome problems associated with such impactors becoming misshapen. The twin tyre impactor is also detailed.

This Technical Specification also describes the test equipment, excluding the impactor. A method of calibrating the test frame is given. The benefit of calibrating the test equipment is the increased reproducibility of the test results.

This Technical Specification also details the classification of glass products. The classification system allows information on the following to be given:

- a) the maximum drop height at which the glass either did not break or broke safely, i.e. in a manner similar to laminated glass or toughened glass;
- b) the manner in which the glass would break, i.e. as toughened glass, laminated glass, annealed glass, irrespective of whether or not the glass was broken during the test;
- c) the maximum drop height at which the glass either did not break or broke safely, i.e. in a manner similar to laminated glass.

This Technical Specification does not specify the intended use of the products, but provides a method of classification in terms of the performance of the materials being tested. The impact energy used for the various levels of classification are designed to provide the intended user or the legislator with the information to assist in defining the level of safety and protection required relative to the intended location at which the selected safety glass is to be used.

NOTE The eventual aim is to develop an International Standard covering the pendulum impact testing of safety glass for use in building. Such a standard could be cited as a normative reference, e.g. in ISO 12543-2^[3].

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 48, *Rubber, vulcanized or thermoplastic — Determination of hardness (hardness between 10 IRHD and 100 IRHD)*

ISO 2408, *Steel wire ropes for general purposes — Minimum requirements*

ISO 4251-1, *Tyres (ply rating marked series) and rims for agricultural tractors and machines — Part 1: Tyre designation and dimensions, and approved rim contours*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

safety glass

glass, which if fractured, gives fragments which are less likely to pierce or to cause severe cuts than fragments of ordinary annealed glass

NOTE Adapted from ISO 6345:1990^[1], 6.4.

EXAMPLE Laminated glass and wired glass.

3.2

safety glazing material

glazing material so constructed, treated or combined with other materials that, if broken by accidental human contact, the likelihood of cutting and piercing injuries that might result from such contact is minimized

3.3

soft body impactor

impactor that is representative of a human body

EXAMPLE A soft body impactor can be either a shot bag (see 6.1.3.1) or a twin tyre (see 6.1.3.2) type.

3.4

asymmetric material (1)

glass that has different surface characteristics on opposite faces, e.g. patterning, coating

3.5

asymmetric material (2)

glass manufactured from laminations of glass or plastics glazing sheet material together with interlayer materials that are arranged in different sequential order and of varying thicknesses

3.6

drop height

vertical height from the horizontal centre line of the impactor at the point of release to the horizontal centre line of the impactor when at rest vertically

3.7

crack-free particle


piece of glass that does not contain any cracks that run from one edge to another

NOTE See Figure 1.

3.8

masking

temporary protective covering applied to the test piece for ease of transportation

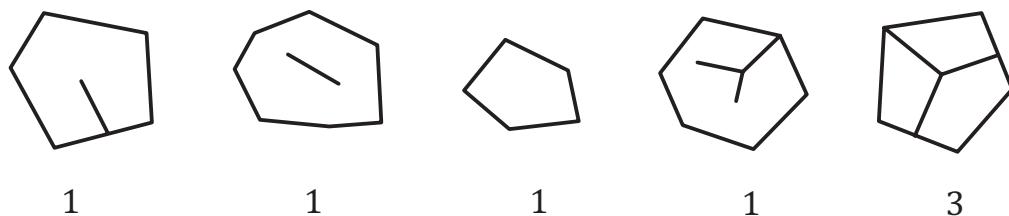**Key**

1, 3 numbers of crack free particles in each piece of glass

Figure 1 — Example of crack free particles

4 Principle

Accidental human impact with glass panes can be a source of injury. The classification of glass in terms of its ability to withstand impact and the consequences of the glass breaking under such impact has been considered in many countries. The use of a soft body impactor to represent a human body has enabled regulators, code officials, and other control organizations to specify glazing that reduces the risk of cutting and piercing injuries. The test method defines the safe breakage characteristics for different types of glass (see Clause 5).

It is the intent of this Technical Specification to bring together the latest technology and understanding of how safety glass is to be tested and to evaluate and classify the result. The test provides a means of determining the retention characteristics and performances of various types of safety glazing materials.

5 Test requirements

5.1 When tested by the method given in Clause 6, each test piece shall either not break or shall break as defined in either 5.2 or 5.3.

5.2 Numerous cracks appear, but no shear or opening is allowed within the test piece through which a (76 ± 1) mm diameter sphere can pass when a maximum force of 25 N is applied (in accordance with Annex C).

Additionally, if particles are detached from the test piece up to 3 min after impact, they shall, in total, weigh no more than the mass equivalent to 10 000 mm² of the original test piece. The largest single particle shall weigh no more than the mass equivalent of 4 400 mm² of the original test piece.

5.3 The ten largest crack-free particles collected within 3 min after impact shall weigh no more than the mass equivalent of 6 500 mm² of the original test piece.

6 Test method


6.1 Test apparatus

6.1.1 Main frame, constructed from welded or bolted, hot-rolled steel channel sections with rounded edges, designed to present a rigid and flat surface to the sub-frame. See Figures 2 and 3. The lower cross members shall be securely fixed to a concrete floor.

NOTE Additional support to the frame can be provided, if required, by means of horizontal steel sections fixed to an adjacent rigid wall (see Figure 2, key item 4).

The dimensions of the main frame (see Figure 4) shall be:


- internal width: (847 ± 5) mm;
- internal height: $(1\,910 \pm 5)$ mm.

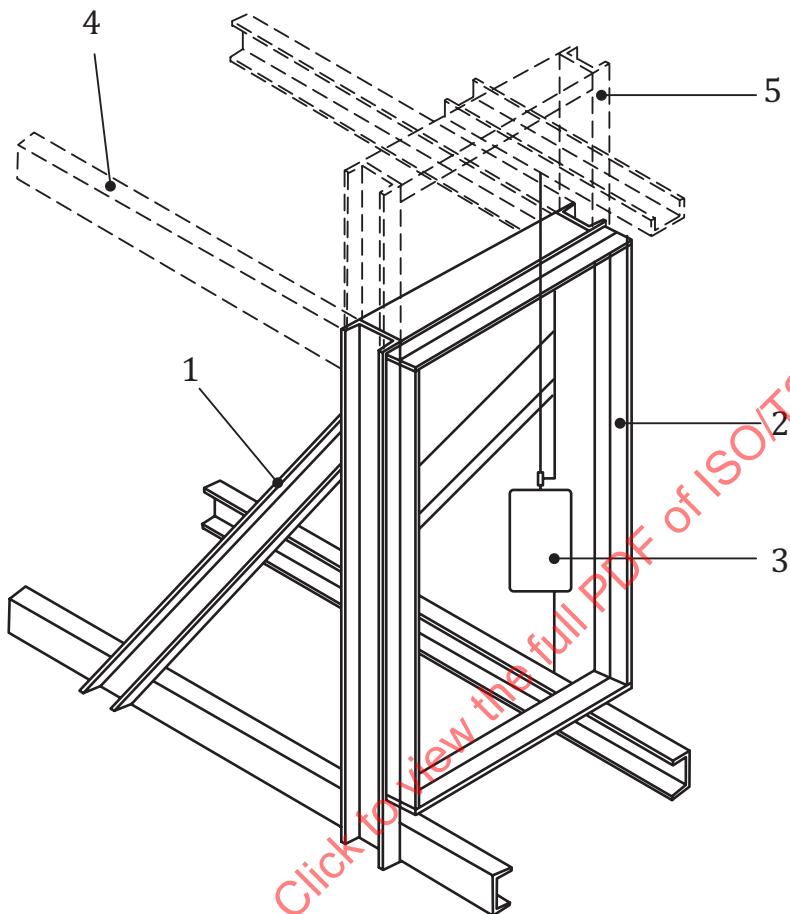

Key

| | |
|---|----------------------------|
| 1 | main frame |
| 2 | clamping frame |
| 3 | impactor |
| 4 | optional support member |
| 5 | optional suspension device |

Figure 2 — Test frame

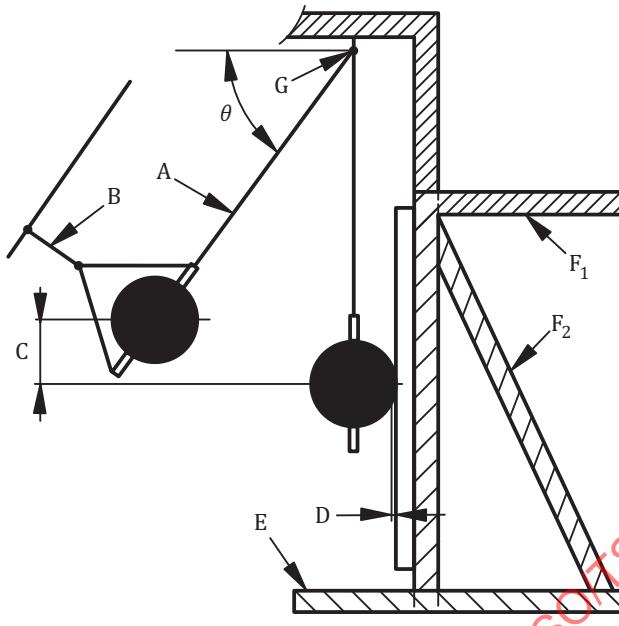**Key**

- A suspension cable
- B traction cable
- C drop height
- D impactor distance from sample
- E support member
- F₁ optional support member
- F₂ cross members
- G bracket ($5 \text{ mm} \leq d \leq 15 \text{ mm}$)
- θ impactor angle from horizontal

Figure 3 — Side elevation of the main frame with the impactor

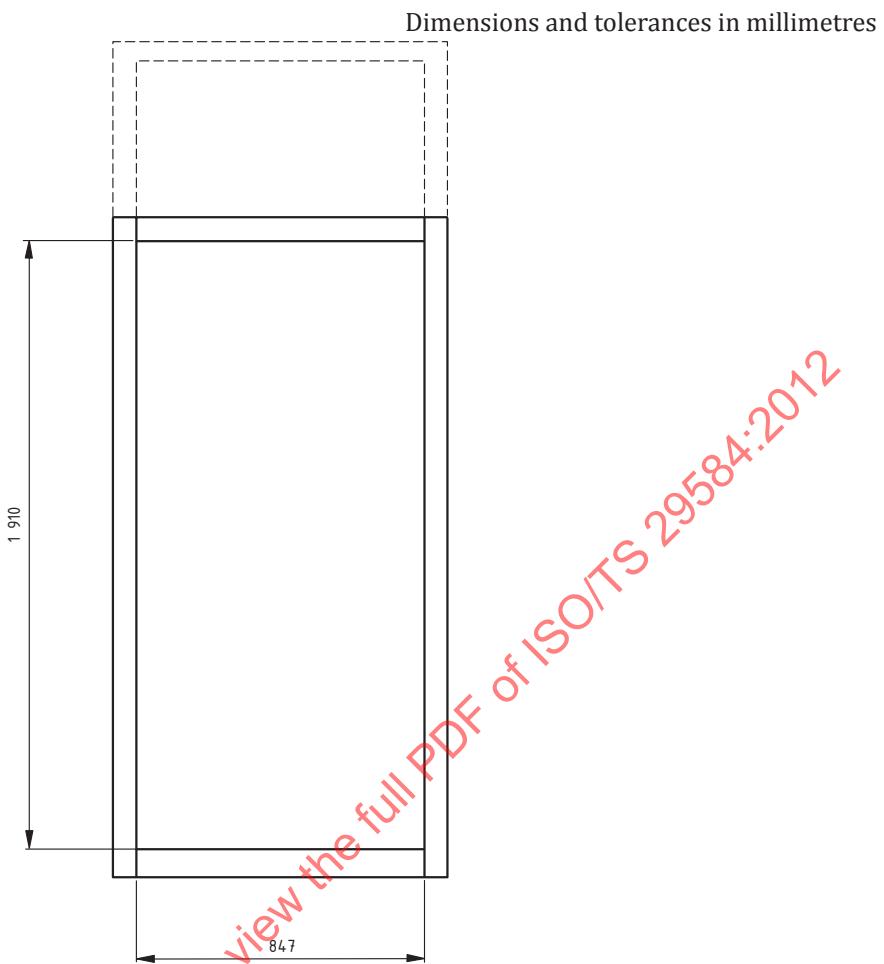


Figure 4 — Dimensions of the front elevation of the frame

6.1.2 Clamping frame, fitted on to the main frame and used to hold the test piece in position for the duration of the test, consisting of two rectangular parts which clamp the test piece along its perimeter. See Figure 5. The inner part of the clamping frame is attached to the main frame.


The assembly is held together by a clamping device. The clamping frame shall be suitably rigid to withstand the pressure exerted by the clamping device.

The dimensions of the clamping frame shall be:

- internal width: (847 ± 5) mm;
- internal height: $(1\,910 \pm 5)$ mm.

Each part of the clamping frame shall be fitted with a strip of rubber. The rubber strips shall be the only element in contact with the test piece and shall be (20 ± 2) mm wide and (10 ± 1) mm thick and have a hardness of (60 ± 5) IRHD in accordance with ISO 48.

NOTE Polychloroprene (neoprene) or a similar material is suitable.

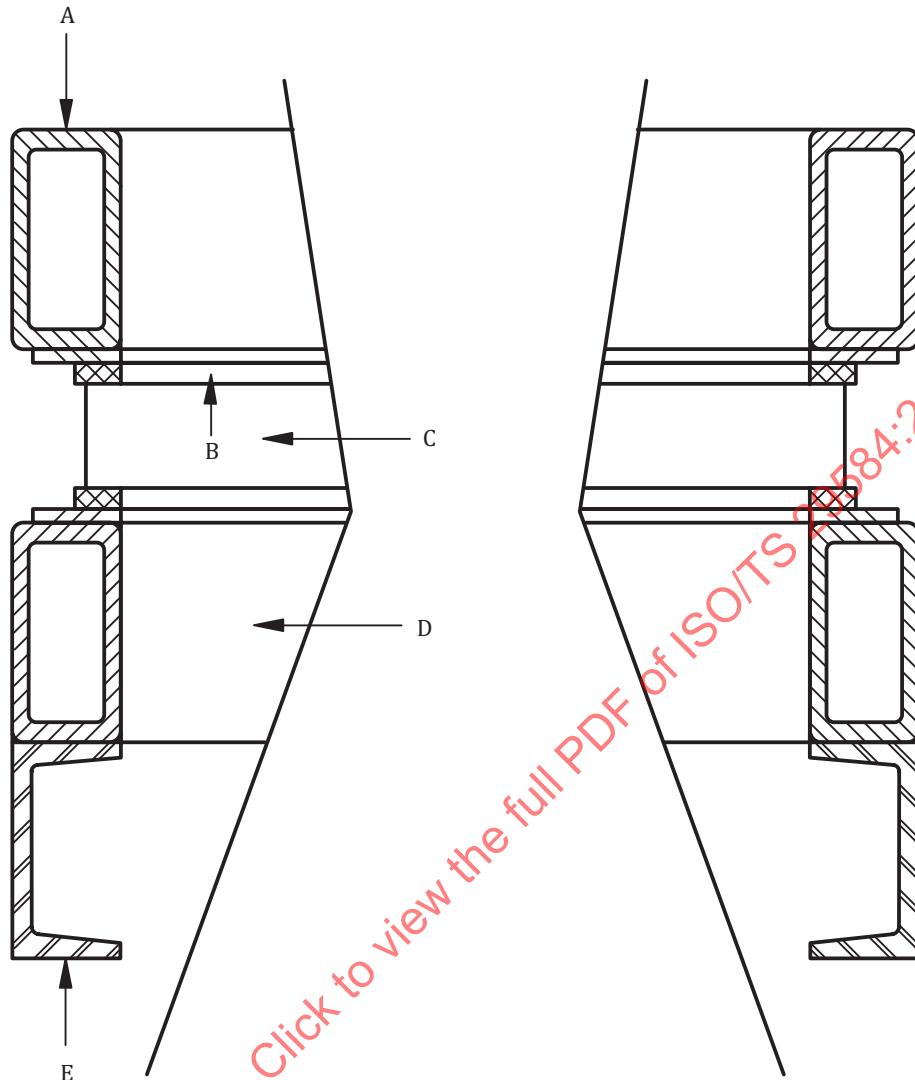**Key**

- A clamping frame e.g. $\sim 100 \text{ mm} \times 50 \text{ mm} \times 8 \text{ mm}$
- B rubber strips $(20^{+2}) \text{ mm} \times (10 \pm 1) \text{ mm}$
- C test piece
- D outer part of the main frame e.g. $\sim 100 \text{ mm} \times 50 \text{ mm} \times 8 \text{ mm}$
- E inner part of the main frame e.g. $\leq 100 \text{ mm} \times 50 \text{ mm}$

Figure 5 — Example of clamping of the test piece

6.1.3 Impactor, of type 6.1.3.1 or 6.1.3.2, suitable for use with the suspension device (6.1.4) and release mechanism (6.1.5).

6.1.3.1 Lead shot bag.

6.1.3.1.1 General description. The bag (see Figure 6a) is a reinforced leather bag filled with chilled lead shot of diameter $(2,5 \pm 0,1) \text{ mm}$ providing a total mass of $(45 \pm 0,1) \text{ kg}$. See Figure 6a. The bag is constructed of 1,5 mm thick pliable leather.

6.1.3.1.2 Method of manufacture. See Annex A.


6.1.3.1.3 Maintenance. Inspect the shot bag impactor at intervals of 1 000 impacts and calibrate as required. If the tape of the impactor is damaged (e.g. when glass fibres are apparent, or the leather bag is visible), it shall be removed and replaced according to Annex A. When the deformation of the impactor is beyond the tolerances, the impactor shall be reshaped manually. If the impactor cannot be restored to within the tolerances, it shall be replaced.

Remove all glass particles embedded in the surface of the impactor.

The tolerances of dimensions for the impactor are shown in Figure 6a.

STANDARDSISO.COM : Click to view the full PDF of ISO/TS 29584:2012

Dimensions and tolerances in millimetres

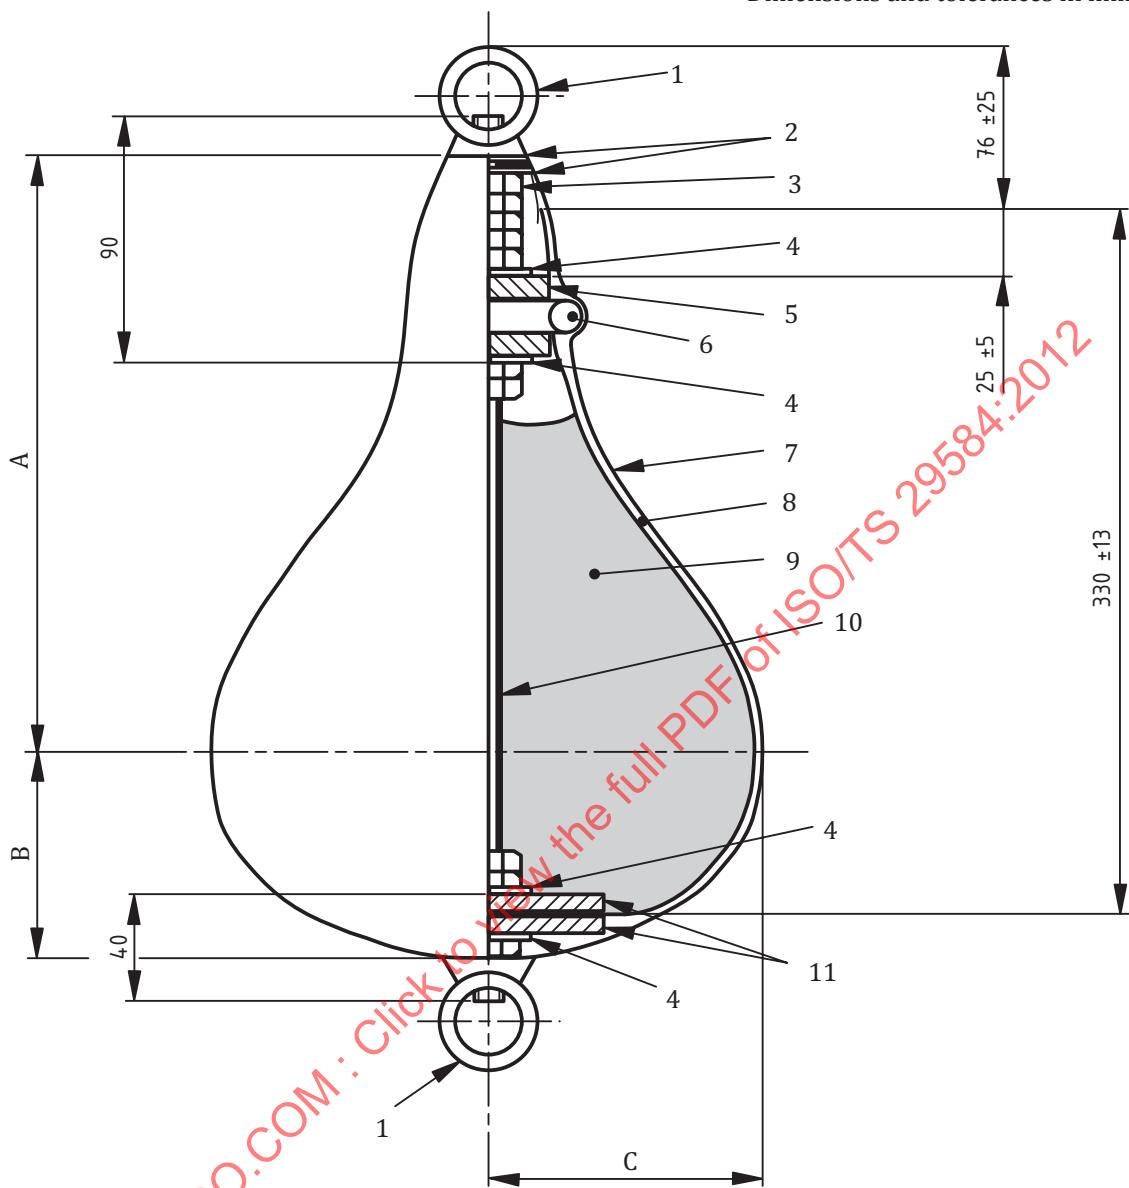**Key**


| | No. required | Remarks |
|---|---------------------|---|
| 1 eye nut | 2 | M10 |
| 2 plane washer | 2 | M10 |
| 3 hexagonal nut | 10 | M10 |
| 4 spring washer | 4 | M10 |
| 5 sleeve nut | 1 | length: 25 mm; diameter: 32 mm |
| 6 hose clamp | 1 | |
| 7 glass fibre-reinforced adhesive polyester tape (see Note 2) | 3 rolls | width: 12 mm; thickness: 0,15 mm |
| 8 leather bag | 1 | synthetic leather (see Note 1) |
| 9 lead shot | ~45 kg | chilled shot, diameter: (2,5 ± 0,1) mm |
| 10 threaded metal rod | 1 | M10 Length : 400mm |
| 11 metal washer | 2 | Thickness: 4,8 ± 1,6mm Diameter: 76 ± 3mm |

NOTE 1 The bag is made of synthetic leather of thickness 1,5 mm by seaming up with two sheets of piece A [see Figure 6 b)] and four sheets of piece B. The margin to seam between pieces A and B is about 4 mm. The Model SB-4500 is the trade name of a product supplied by Wining KK. This information is given for the convenience of users of this document and does not constitute an endorsement by ISO of the product named. Equivalent products may be used if they can be shown to lead to the same results.


NOTE 2 3 M N° 898 is the trade name of a product supplied by 3M Company. This information is given for the convenience of users of this document and does not constitute an endorsement by ISO of the product named. Equivalent products may be used if they can be shown to lead to the same results.

Figure 6a — Plan of Shot Bag Impactor

Dimensions of pieces A

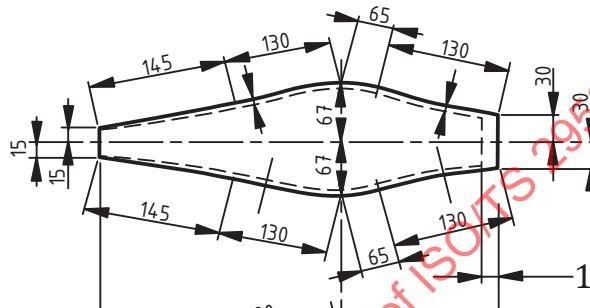

Dimensions of pieces B

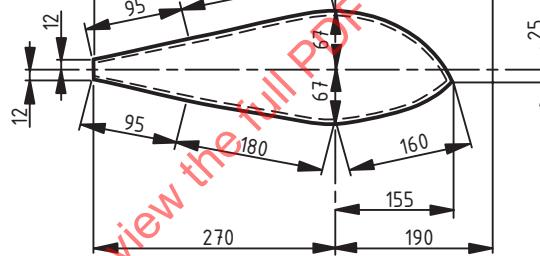

Key

1 Margin to seam 16 mm

Figure 6b — Dimensions of pieces of Shot Bag Impactor

6.1.3.2 Twin tyre impactor

6.1.3.2.1 General description. Impactor consisting of two pneumatic tyres, e.g. tyre 3.50-8/4PR¹⁾ or Continental T7, in accordance with ISO 4251-1, with round section and flat longitudinal tread. See Figure 7. The tyres shall be fitted to the rims of the wheels that carry two equal steel masses. The masses shall be dimensioned so that the total mass of the impactor is $(50 \pm 0,1)$ kg.

NOTE The tyre specified for this impactor, while in accordance with ISO 4251-1, has been found to have performance variations dependent on site and country of manufacture. This variation can cause problems with the calibration, but has not been found to affect product classification.


6.1.3.2.2 Method of manufacture. An example of the impactor, using steel with a density of 7 830 kg/m³, is shown in Figure 7.

1) Tyre 3.50-8/4PR (reference V47, V60, and V64) and Continental T7 are examples of suitable products available commercially. This information is given for the convenience of users of this document and does not constitute an endorsement by ISO of these products.

6.1.3.2.3 Maintenance. Check the air pressure in the tyres in accordance with 6.4.3.

Remove all glass particles embedded in the surface of the tyres.

Inspect the state of the tyres regularly and replace when required.

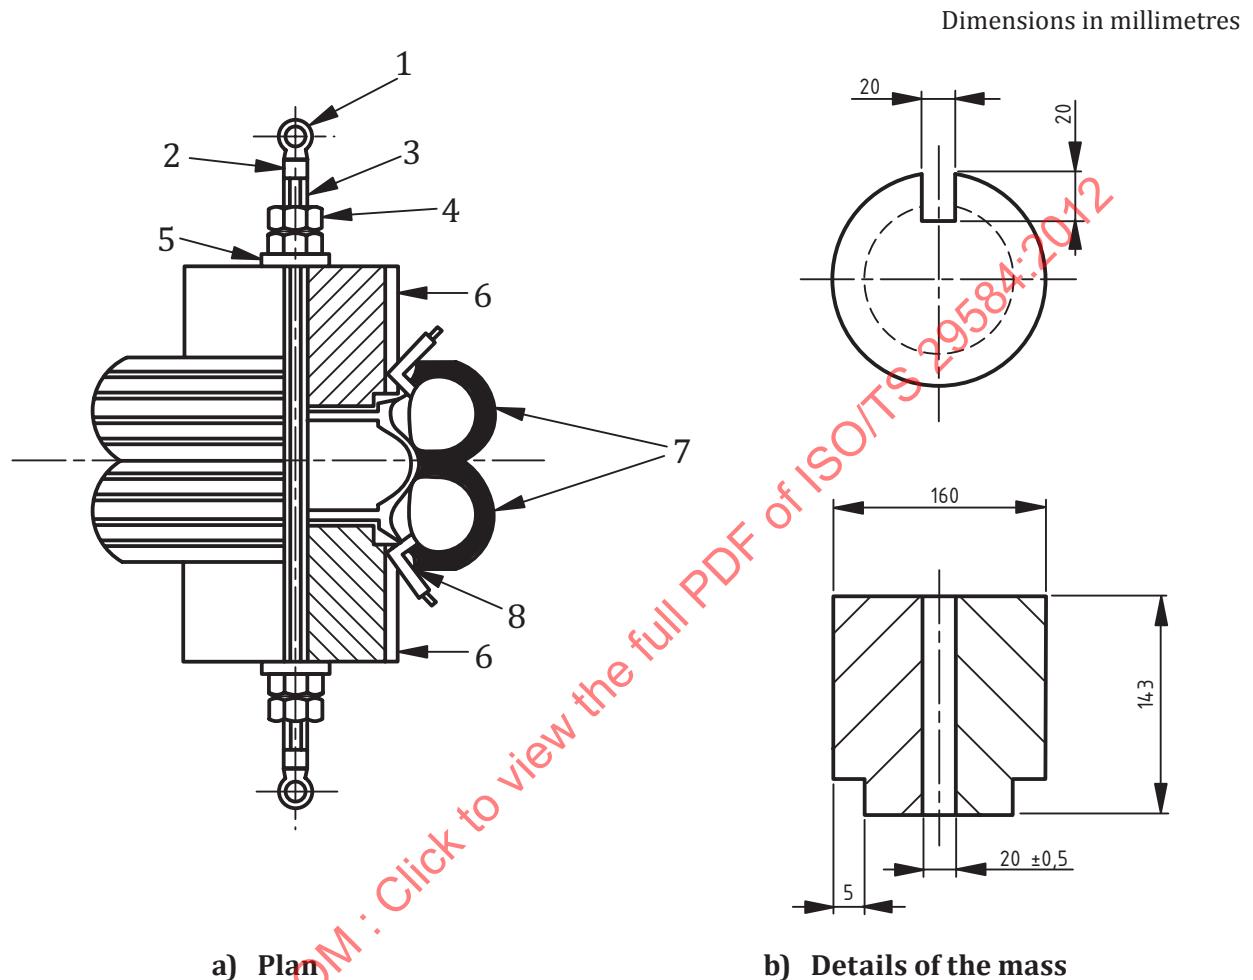

Key

| | | No. required. | Remarks |
|---|---|----------------------|------------------------------|
| 1 | eye bolt | 2 | M20 |
| 2 | hexagonal nut | 2 | M20 |
| 3 | screw spindle | 1 | M20 45 mm |
| 4 | hexagonal nut | 4 | M20 |
| 5 | collar | 4 | |
| 6 | mass of density 7 830 kg/m ³ | 2 | See Figure 7 b) |
| 7 | pneumatic tyre | 2 | Tyre 3.50-8/4PR ² |
| 8 | rim | 2 | 250 - 8 |

Figure 7 — The twin tyre impactor

6.1.4 Suspension device. The impactor shall be suspended by means of a steel cable of diameter 5 mm conforming to ISO 2408, from a bracket attached above the head of the main frame. The bracket shall be

rigid to ensure that the point of suspension remains stationary during the test and shall be positioned to permit the impactor to strike the centre of the test piece.

At the highest drop height, the angle, θ , between the taut suspension cable and the bracket shall not be less than 14° (see Figure 3).

When the impactor is hanging freely, at rest, the distance between the impactor and the surface of the test piece, d , shall not exceed 15 mm and shall not be less than 5 mm (see Figure 3) and the centre of area of contact of the impactor shall be within 50 mm vertically and horizontally from the centre of the test piece.

6.1.5 Traction and release system. The impactor release mechanism enables the impactor to be raised and positioned at each of the specified drop height positions, and then to be released so that it swings freely and impacts the test piece. The release cable shall be connected to the top and bottom ends of the impactor by suitable links so that the raising force is applied at right angles to the axis of the impactor. The release mechanism shall ensure that the release cable is maintained at the correct orientation at each of the drop heights. An example of a release mechanism is given in Annex F.

6.2 Calibration of test apparatus

The test apparatus shall be calibrated in accordance with Annex B in order to ensure that the energy transferred to the test piece by the impactor during the test carried out on a different apparatus is consistent.

6.3 Test pieces

6.3.1 General

Each test piece shall comprise a single pane of glass product and be representative of the normal production of the type of product submitted for test.

6.3.2 Dimensions of the test pieces

The test pieces shall have the following dimensions:

- a) width: (876 ± 2) mm;
- b) height: $(1\ 938 \pm 2)$ mm.

Results obtained with test pieces of these dimensions are valid for classification purposes of the glass product whatever the service dimensions.

6.3.3 Number of test pieces

The test shall be carried out at each drop height on four pieces of identical structure and the same nominal thickness.

If the test pieces are of an asymmetric material, their number shall be doubled unless they are intended solely for installation in situations where the risk of impact is from one side only.

6.3.4 Preparation of the test pieces

Remove all masking and protection material from the test pieces and condition for a minimum of 12 h at $(20 \pm 5)^\circ\text{C}$.

6.4 Impact test procedure

6.4.1 Testing shall start at the lowest drop height (see Table 1) and increase up to the drop height appropriate to the class for which the material is intended (see 7.2).

6.4.2 The test shall be carried out at $(20 \pm 5)^\circ\text{C}$, i.e. room temperature.

6.4.3 Place each test piece in the clamping frame so that its edges are encased in the rubber to a minimum depth of 10 mm. The test piece shall be firmly clamped within the sub frame.

Inflate both impactor tyres to a pressure of $(0,35 \pm 0,02)$ MPa. Pressure shall be checked prior to testing and every 4 h after the start of the test.

Raise the impactor to the lowest drop height (see Table 1) and stabilize. At the drop height, the suspension cable shall be taut, and the axis of the impactor and cable shall be in line (see Figure 3).

Table 1 — Impact levels

| Classification | Lead shot bag mm | Twin tyre mm |
|----------------|---------------------|-----------------|
| 3 | 300 | 190 |
| 2 | 450 | 450 |
| 1 | 1 200 | 1 200 |

6.4.4 Release the impactor so that it falls with a pendular movement and without initial velocity. The direction of impact on the centre of the test piece shall be normal to the surface. If the impactor strikes the test piece more than once the test shall be deemed to be invalid.

The masses of the twin tyre impactor shall not make contact with the test piece during the impact.

6.4.5 For asymmetric materials that are intended for installation where the risk of impact is from both sides, carry out the test on both sides.

For asymmetric materials where the required classification is for one face only, then solely the designated face shall be tested and this shall be reported in the test report.

6.4.6 Inspect the test piece after impact and note whether:

- it remains unbroken;
- it broke in accordance with either the requirements of 5.2 or 5.3;
- it broke and failed to conform to the requirements of 5.2 or 5.3.

6.4.7 If any of the initial four test pieces fails to conform to the requirements of 5.2 or 5.3, terminate the procedure. If all four test pieces either do not break or else break according to the criteria given in 5.2 or 5.3, and it is required by the manufacturer to test the material to a higher impact level, increase the drop height to the next level (see Table 1). Repeat the test on four more samples of the same material.

If the material remained unbroken, the same sample(s) may be used.

6.4.8 Report all test results in accordance with Clause 8.

7 Classification

7.1 General

Glass conforming to this Technical Specification is classified in accordance with:

- its performance under the impact test;

- b) the drop height at which breakage occurred;
- c) the drop height at which the product satisfied the specifications of 5.2;
- d) the drop height at which the product satisfied the specifications of 5.3.

7.2 Drop height class

Glass shall be classified as follows:

- a) **Class 3** — material that conforms to the requirements of 5.2 or 5.3 when tested by the method given in 6.4 at a drop height of 190 mm with the double tyre impactor or 300 mm with the lead shot bag;
- b) **Class 2** — material that conforms to the requirements of 5.2 or 5.3 when tested by the method given in 6.4 at drop heights of 190 mm with the double tyre impactor or 300 mm with the lead shot bag and 450 mm with both impactors;
- c) **Class 1** — material that conforms to the requirements of 5.2 or 5.3 when tested by the method given in 6.4 at drop heights of 190 mm with the double tyre impactor or 300 mm with the lead shot bag, 450 mm with both impactors and 1 200 mm with both impactors.

7.3 Mode of breakage

If all test pieces remain unbroken at the drop height appropriate to its intended drop height class, the mode of breakage shall be determined as per Annex E. The mode of breakage shall be described as follows:

- a) Type A — Numerous cracks appear forming separate fragments with sharp edges, some of which are large;
- b) Type B — Numerous cracks appear, but the fragments hold together and do not separate;
- c) Type C — Disintegration occurs, leading to a large number of small particles which are relatively harmless.

NOTE The descriptions of the mode of breakage are intended to convey the following information (see Annex E):

- Type A — mode of breakage typical of annealed glass;
- Type B — mode of breakage typical of laminated glass and wired glass;
- Type C — mode of breakage typical of toughened glass.

7.4 Performance classification

The performance classification of a glass product shall be given as follows:

$\alpha(\beta)\varphi$

where

- α is the highest drop height class (7.2) at which the product either did not break or broke in accordance with 5.2 or 5.3;
- β is the mode of breakage;
- φ is the highest drop height class (7.2) at which the product either did not break or when it did break, broke in accordance with 5.2.

The retention criterion, φ , is met when no break occurs or numerous cracks appear, but no shear or opening is allowed within the test piece through which a (76 ± 1) mm diameter sphere can pass when a maximum force of 25 N is applied in accordance with Annex C.

When a glass product breaks at a drop height of 190 mm with a double tyre impactor or 300 mm with a lead shot bag and the breakage is not in accordance with 5.2, then the value of φ quoted shall be zero.

EXAMPLE 1

A set of laminated glass test pieces were impacted with the following results:

- at 190 mm/300 mm: three test pieces did not break while one test piece broke in accordance with 5.2;
- at 450 mm: all four test pieces broke in accordance with 5.2;
- at 1 200 mm: all four test pieces broke and failed to comply with 5.2 or 5.3.

Classification: 2(B)2

EXAMPLE 2

A set of thermally toughened soda lime silicate glass test pieces were impacted with the following results:

- at 190 mm/300 mm: all four test pieces did not break;
- at 450 mm: all four test pieces broke in accordance with 5.3;
- at 1 200 mm: all four test pieces broke in accordance with 5.3.

Classification: 1(C)3

EXAMPLE 3

A set of thermally toughened soda lime silicate glass test pieces were impacted with the following results:

- at 190 mm/300 mm: two test pieces did not break and two test pieces broke in accordance with 5.3;
- at 450 mm: all four test pieces broke in accordance with 5.3;
- at 1 200 mm: all four test pieces broke in accordance with 5.3.

Classification: 1(C)0

8 Test report

The test report shall contain at least the following information:

- a) type and nominal thickness of the glass product;
- b) dimensions of test pieces;
- c) the test method used, with reference to this Technical Specification (ISO/TS 29584:2012);
- d) behaviour at each drop height for each test piece, including whether the test piece broke;
- e) if the test piece broke, the mode of breakage, and whether breakage was in accordance with the criteria of 5.2, 5.3 or neither;
- f) performance classification and type of impactor used: twin tyre or lead shot bag;
- g) date of the last calibration of the test rig according to Annex B;
- h) in the case of applied films, whether the film was clamped in the frame;

- i) the name and the address of the testing laboratory;
- jj) test identification to enable test data to be traced;
- k) date of test report;
- l) name of manufacturer, processor, and supplier of the test material;
- m) declared description of the material tested (including product type, trade name or other means of identification);
- n) in the case of asymmetric materials, the classification of both surfaces unless only one impact side has been tested, in which case the classification and the surface that was impacted shall be reported.

STANDARDSISO.COM : Click to view the full PDF of ISO/TS 29584:2012

Annex A

(normative)

Method of fabrication of the shot bag impactor

A.1 Figure 6 shows all the materials required for fabricating a shot bag (also called punch bag) along with the respective dimensions. The dimensions indicated on the right side of Figure 6a are those specified in this Technical Specification. The dimensions indicated on the left side of Figure 6a are those required for fabricating a shot bag. A shot bag compliant with this Technical Specification can be fabricated by placing the upper double nut position at 90 mm from the top of the bag and the lower double nut position at 40 mm from the bottom of the bag.

A.2 Before starting, loosen the strap of the punch bag and remove the internal rubber bag.

A.3 At the hanging strap position of the bag, provide a hole with a knife in a size to allow a threaded metal rod of diameter 10 mm to pass through.

A.4 Install two hexagonal nuts 3 at about 90 mm from the upper end of the threaded metal rod to form a double nut (for locking) and fix them securely in place. Next, at the upper side of double nut, install a spring washer 4, a sleeve nut 5, a spring washer 4 and a nut 3 and fix them. Then install four nuts 3 fastening them retrospectively.

A.5 At 40 mm from the other end of the threaded metal rod 10, form a double nut using hexagonal nut 3 to fix the rod in place. Install a spring washer 4 and metal washer 11 and thrust the rod 10 through the centre of the bottom of the punch bag 8 from inside.

A.6 Install metal washer 11 and spring washer 4 on the threaded metal rod extruding out of the bottom of the punch bag, fasten with a hexagonal nut 3 forming a double nut in combination with an eye nut 1, and fix the rod in place. (For safety during testing, if the end of the threaded metal rod does not extrude from the eye nut due to any thickness error with the metal or spring washers, change the distance from the end from 40 mm to 45 mm and repeat steps A.5 and A.6.)

A.7 At the other end of the rod, install plain washer 2 and thrust the rod through the hanging strap. Install plain washer 2, then fasten with eye nut 1 (As in step A.6, if the end of the rod does not extrude through the eye nut, change the distance from the upper end from 90 mm to about 95 mm and redo steps A.3 and A.6.)

The five nuts above sleeve nut 5 and plain washer 2 are to hang the punch bag following the specified dimensions.

A.8 Fix the lace from the bottom up to about half of the total lacing length.

A.9 Place the punch bag (A.8), three rolls of tape, and hose clamp 6 on a spring balance, then fill the bag with lead shots until the mass of the total assembly reaches $(45,0 \pm 0,1)$ kg.

A.10 Fix the remaining lace, and fasten the sleeve nut section of the punch bag neck with hose clamp 6.

A.11 Hang the completed punch bag weighing $(45,0 \pm 0,1)$ kg with a rope from the ceiling or other elevated section.


A.12 Tape the punch bag to cover its entire surface using three rolls of the specified type of tape in diagonal, overlapping manner. Tape the neck section separately. (The “neck” refers to the section extending from the top of the bag to about 120 mm downward.)

A.13 to A.26 describes the taping procedure.

A.13 Shape the lifted bag properly by tapping with the hand.

A.14 Measure the circumference of the section where the diameter is the maximum and calculate the diameter. The maximum diameter shall be about 250 mm. (If the maximum diameter significantly deviates from the specified value, there is no way to correct it. In that case, the only solution is probably to replace the bag with another one or remake the shot bag.)


A.15 Assign code I to the leather seam on which the lace is located. Assign codes II, III, IV, V and VI to the other seams counter clockwise from code I (see Figures A.1 and A.2).

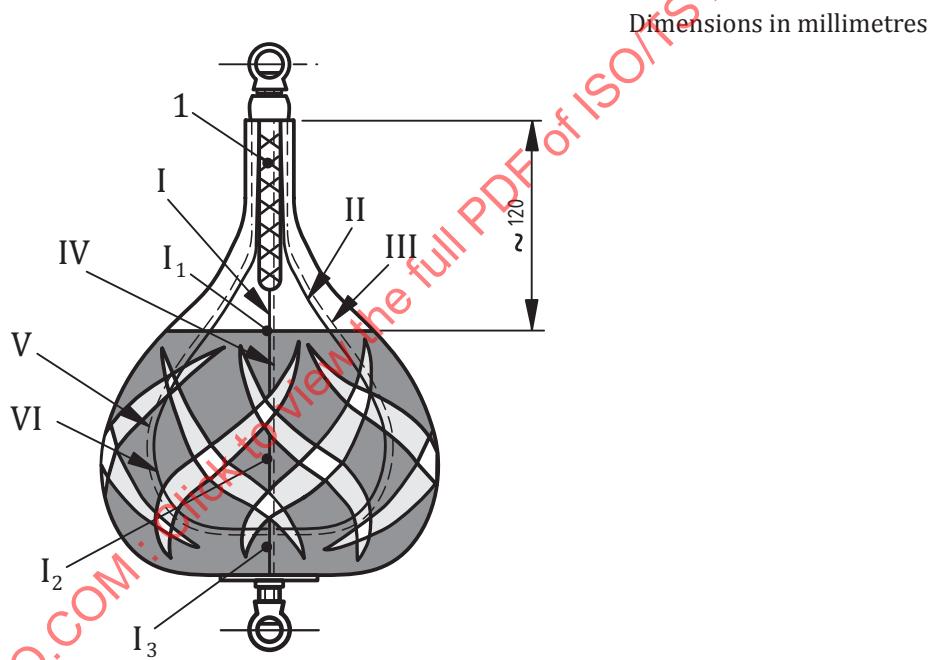

Key

| | | | |
|-----|---------------------------------|----------------|---|
| I | lace | V | seam 5 (at the back of the bag) |
| I | seam 1 (includes lace) | VI | seam 6 |
| II | seam 2 | I ₁ | taping point 1 on seam 1 (at base of neck portion, 30 mm from lace portion) |
| III | seam 3 (at the back of the bag) | I ₂ | taping point 2 on seam 1 (at maximum circumference) |
| IV | seam 4 (at the back of the bag) | I ₃ | taping point 3 on seam 1 (30 mm outside the metal washer) |

Figure A.1 — Side Elevation of shot bag (taping points are only shown on one seam but they are on all seams)

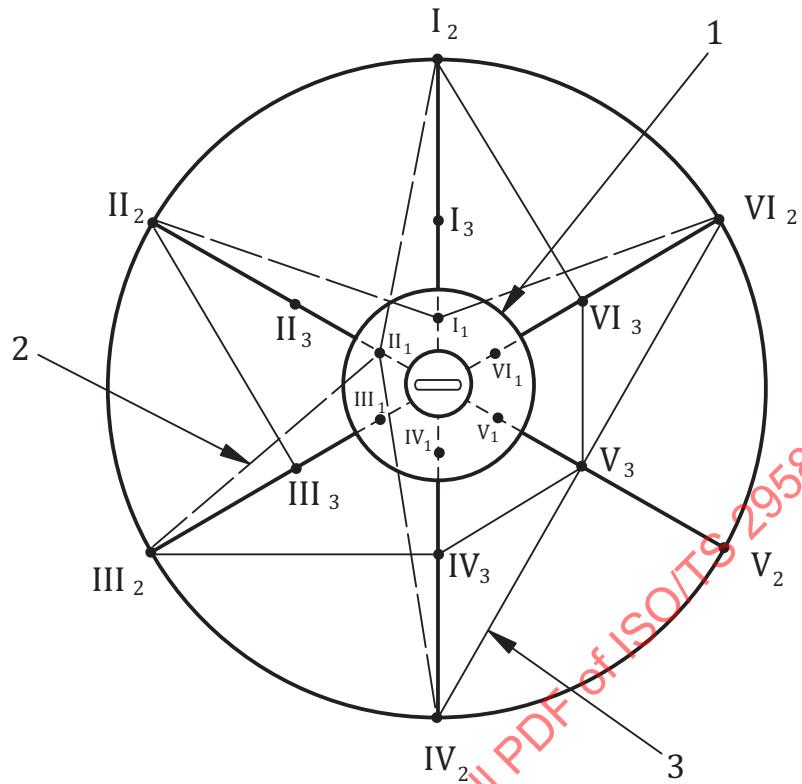**Key**

| | |
|--|--|
| 1 | metal washer |
| 2 | example taping lines on upper part of bag |
| 3 | example taping lines on lower part of bag |
| I ₁ , II ₁ , III ₁ , IV ₁ , V ₁ , VI ₁ | upper taping points 1 (30 mm below lace) on seams I-VI |
| I ₁ , II ₁ , III ₁ , IV ₁ , V ₁ , VI ₁ | middle taping points 2 (at maximum circumference) on seams I-VI |
| I ₃ , II ₃ , III ₃ , IV ₃ , V ₃ , VI ₃ | lower taping points 3 (30 mm outside the metal washer) on seams I-VI |

Figure A.2 — Plan of shot bag from below

A.16 As shown in Figures A.1 and A.2, assign code I₁ to the section about 30 mm below the lower end of the lace section, code I₂ to the section with the maximum diameter, code I₃ to the section about 30 mm outside the metal washer. In the same manner, assign code II₁, II₂, II₃, III₁, III₂, III₃ and so on through VI₁, VI₂ and VI₃ in sequence.

A.17 Start taping at I₁ by applying it diagonally at an angle of 45 degrees to reach point III₃ via point II₂. The tape should be lightly extended without any strain on it. Cut the tape at point III₃.

A.18 In the same manner, apply the tape lightly, without strain, to cover points II₁, III₂ and IV₃; III₁, IV₂ and V₃; IV₁, V₂ and VI₃; V₁, VI₂ and I₃; and VI₁, I₂ and II₃, cutting the tape at the end of each sequence.

A.19 Next, slant the tape by 45 degrees in the opposite direction and tape the bag, covering I₁, VI₂ and V₃; II₁, I₂ and VI₃; III₁, II₂ and I₃; IV₁, III₂ and II₃; V₁, IV₂ and III₃; and VI₁, V₂ and IV₃ in the same manner as in steps A.17 and A.18.

A.20 Around the tape applied (A.19), apply the tape in two rows on the right and left sides, completing twofold taping in total five rows, also without strain.

Figure A.1 shows the view as taping is completed to this point. The sections shaded in darker grey are where the tape is applied in five rows and overlapped in four layers while the sections shaded in lighter grey where the tape is applied in twofold five rows.


The total tape consumption up to this point amounts to 0,8 to 0,9 of a roll.

The following are three tips on taping:

- Avoid neighbouring rows overlapping when carrying out twofold taping in five rows. Overlapping causes wrinkles. In particular, the upper and lower sections of the respective rows can easily overlap. If this happens, tape locations cannot be correctly recognized in the subsequent steps.
- Do allow the tape to be put under strain. Strain hardens the bag.
- Ensure that tapes cross at the section where the diameter is greatest.

A.21 Next, shift the tape by half its width and apply it continuously, without cutting it, to achieve twofold taping in five rows. Start at point I_1 to pass through points II_2 III_3 , IV_3 , V_3 , VI_2 , I_1 in this order (see Figure A.2). Force the tape to be redirected at the bottom of the bag to apply it from point III_3 to point V_3 via IV_3 (Wrinkles are permitted in doing so.) Then turn the taping direction to allow taping from point V_3 to point I_1 via point VI_2 (see Figure A.3).

A.22 From point I_1 where taping ended in the previous step, extend it (wrinkles permitted) to pass through II_1 , III_2 , IV_3 , V_3 , VI_3 , I_2 and II_1 (see Figure A.3). In the same manner, apply the tape to cover III_1 , IV_2 , V_3 , VI_3 , I_3 , II_2 and III_1 ; IV_1 , V_2 , VI_3 , I_3 , II_3 , III_2 and IV_1 ; V_1 , VI_2 , I_3 , II_3 , III_3 , IV_2 and V_1 ; VI_1 , I_2 , II_3 , III_3 , IV_3 , V_2 and VI_1 , then return to I_1 . Then repeat the same procedure again to achieve twofold taping (Figure A.3).

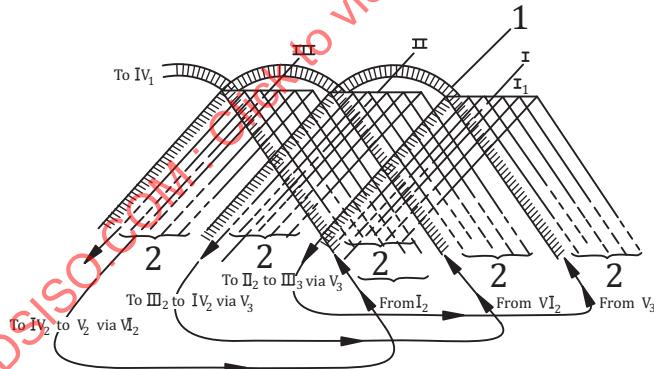

Key

- 1 starting point (shift the tape by half a width)
- 2 five rows twofold


Figure A.3 — Taping method

A.23 As step A.22 is completed, the tape returns to point 1. Next, shift the tape to the right, and follow steps A.21 and A.22 to perform the same procedure and achieve twofold taping in five rows. Never strain the tape and apply it carefully in five rows.

When the steps above are completed, taping is completed in eight folds in five rows over the sections shaded darkly in Figure A.4 and in the lighter-shaded sections, in four folds in five rows. (The total tape consumption up to this point amounts to 1,8 to 1,9 rolls.)

A.24 Reinforce the sections shown in white and lightly shaded areas in Figure A.4 so that taping is achieved in eight folds. To reinforce, apply the tape in four folds and in several rows so that it crosses at the section where the diameter is the greatest. Now the tape is applied in eight folds over the white sections and lighter grey sections (see Figure A.4).

The total tape consumption up to this point amounts to 2,6 to 2,7 rolls.

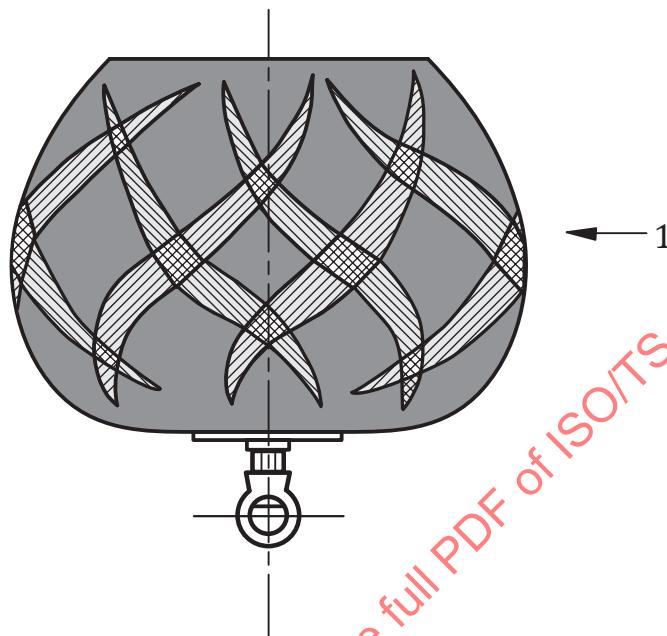

Key

1 Applying the tape in four folds over the “light grey” sections achieves taping at the intersection in eight folds.

Figure A.4 — Taping reinforcement


A.25 As it is specified that the body and neck sections be taped separately, start taping for the neck portion below the upper eye nut to proceed in a spiral manner downward by shifting the tape by half its width until the tape reaches the lace section. (Apply taping until the tape becomes flush with the point already taped in the previous steps up to step A.24.) The “neck” refers to the portion extending from the top of the bag to about 120 mm below. (see Figure A.1).

Taping in a spiral manner causes part of the tape to be not in contact with the bag as shown in Figure A.5. Apply pressure to these parts of the tape so that contact with the bag is established.

Repeat this operation four times to achieve taping in eight folds.

The total tape consumption up to this point amounts to about 2,9 rolls.

A.26 As this annex specifies that taping be performed using three rolls of tape, apply the remaining portion of the tape at random points with allowance given for retention of the tape used for reinforcement so that the tape is evenly applied.

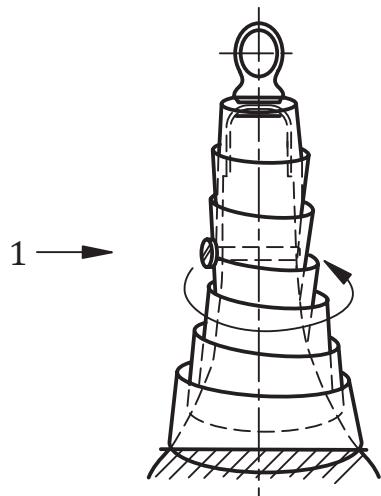

Key

1 Apply the tape in a spiral manner overlapping by half its width.

Figure A.5 — Taping impactor neck (View when taping is completed around the neck)

Annex B (normative)

Calibration of the test rig

B.1 Calibration procedure

B.1.1 The calibration test piece shall be a 10 mm thick pane of thermally toughened soda lime silicate safety glass according to ISO 16293-1^[4] made from soda lime silicate float glass.

The dimensions of the calibration test piece shall be (876 ± 2) mm \times $(1\,938 \pm 2)$ mm.

Remove all masking and protection material from the calibration test piece and condition it for a minimum of 12 h at the calibration temperature of (20 ± 5) °C.

Fix a constantan rosette strain gauge to the centre of the pane in order to measure the horizontal and vertical micro-deformation. The precision strain gauge²⁾ shall be of the following type:

- a) resistance at 24°C: $(350,00 \pm 1,75)$ Ω or $(120,0 \pm 0,6)$ Ω;
- b) length of the grid: 3,18 mm to 5 mm;
- c) width of the grid: 1,4 mm to 4,57 mm.

B.1.2 Place the calibration test piece in the clamping frame so that the strain gauge is on the opposite side to the impact. When clamped, the rubber shall be compressed by not less than 5 % and not more than 10 % of the thickness.

Use either a twin tyre impactor or shot bag impactor.

When using a twin tyre impactor, inflate both tyres to a pressure of $(0,35 \pm 0,02)$ MPa.

Raise the impactor to the lowest drop height and stabilize. At the drop height, the suspension cable shall be taut and the axis of the impactor and cable shall be in line.

B.1.3 Release the impactor, stabilized in the launch position, so that it falls with a pendular movement without initial velocity. The impact shall occur at the centre of the calibration test piece striking it only once.

Measure and record the horizontal and vertical micro-deformation. Record three measurements per drop height.

B.1.4 Repeat the procedure in B.1.3 for each drop height (see Table B.1).

Table B.1 — Drop heights for the calibration test

| Drop height mm |
|-------------------|
| 200 |
| 250 |

2) The CEA-06-125WT-350 is an example of a suitable product available commercially. This information is given for the convenience of users of this International Standard and does not constitute an endorsement by ISO of this product.

Table B.1 (continued)

| Drop height mm |
|--------------------------|
| 300 |
| 450 |
| 700 |
| 1 000 |
| 1 200 |

B.2 Calibration report

The calibration report shall contain at least the following information:

- a) name, address and reference to impact rig;
- b) name of test engineer, date of calibration;
- c) type and nominal thickness of glass;
- d) dimensions of the calibration test piece;
- e) type of impactor;
- f) description of the test rig (material e.g. steel; type of clamping, i.e. continuous, bolted,);
- g) all measured values per drop height;
- h) curves (drop height versus horizontal micro-deformation and drop height versus vertical micro-deformation) based upon the mean values with the type of strain gauge used;
- i) the test method used, with reference to this annex of this Technical Specification (ISO/TS 29584:2012, Annex B).

B.3 Reference calibration curve

The curves obtained after the calibration procedure shall be in accordance with the reference calibration curves within a tolerance of $\pm 10\%$ (see Tables B.2 and B.3, and Figures B.1 and B.2 for a twin tyre impactor and Tables B.4 and B.5, and Figures B.3 and B.4 for a lead shot bag, respectively) in order to ensure that the energy transferred to the test piece by the impactor during the test is equivalent to the energy required for the classification.

B.4 Calibration frequency

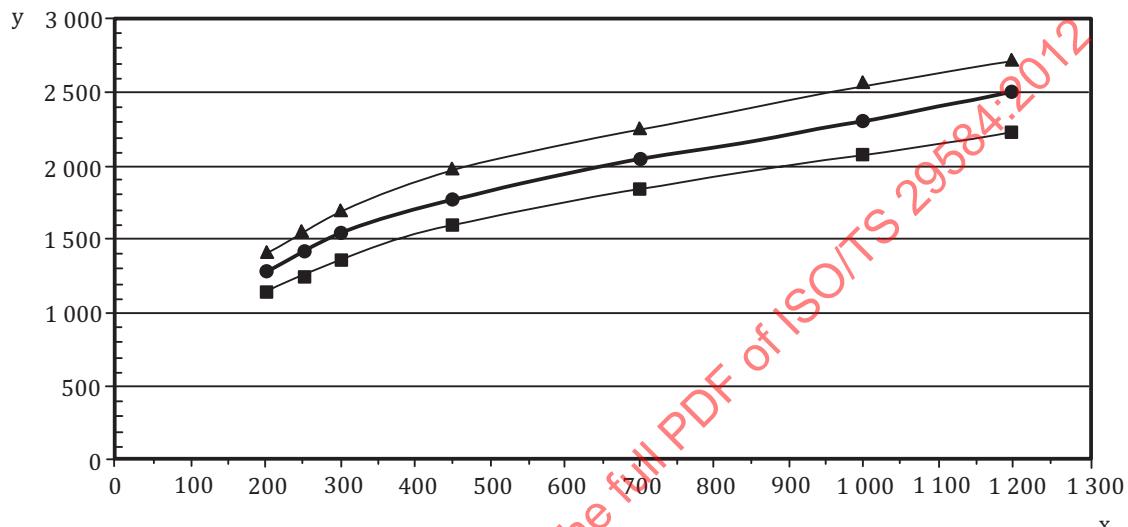
The calibration procedure shall be undertaken every three years. However, if a major change, e.g. change of structural components, clamping system, etc., is made to the rig then it shall be recalibrated prior to testing.

Table B.2 — Reference mean peak horizontal micro-strain for twin tyre impactor

| Drop height mm | Mean value $\varepsilon_{TT,h} \times 10^6$ | Mean value- minus 10 % | Mean value- plus 10 % |
|--------------------------|---|-----------------------------------|------------------------------|
| 200 | 1 275 | 1 147 | 1 402 |
| 250 | 1 418 | 1 276 | 1 559 |
| 300 | 1 542 | 1 388 | 1 696 |

Table B.2 (continued)

| Drop height mm | Mean value $\varepsilon_{TT, h} \times 10^6$ | Mean value- minus 10 % | Mean value- plus 10 % |
|-------------------|---|---------------------------|-----------------------|
| 450 | 1 793 | 1 613 | 1 972 |
| 700 | 2 063 | 1 857 | 2 269 |
| 1 000 | 2 327 | 2 094 | 2 559 |
| 1 200 | 2 503 | 2 252 | 2 753 |


**Key**

- mean value
- mean value minus 10 %
- ▲— mean value plus 10%

x drop height
y mean peak horizontal micro-strain for twin tyre Impactor ($\varepsilon_{TT, h} \times 10^6$)

Figure B.1 — Reference horizontal micro-strain calibration curve for twin tyre impactor**Table B.3 — Reference mean peak vertical micro-strain for twin tyre impactor**

| Drop height mm | Mean value $\varepsilon_{TT, v} \times 10^6$ | Mean value- minus 10 % | Mean value- plus 10 % |
|-------------------|---|---------------------------|-----------------------|
| 200 | 805 | 724 | 885 |
| 250 | 911 | 820 | 1 002 |
| 300 | 1 013 | 912 | 1 114 |
| 450 | 1 181 | 1 063 | 1 299 |
| 700 | 1 389 | 1 250 | 1 528 |
| 1 000 | 1 601 | 1 440 | 1 761 |
| 1 200 | 1 742 | 1 567 | 1 916 |

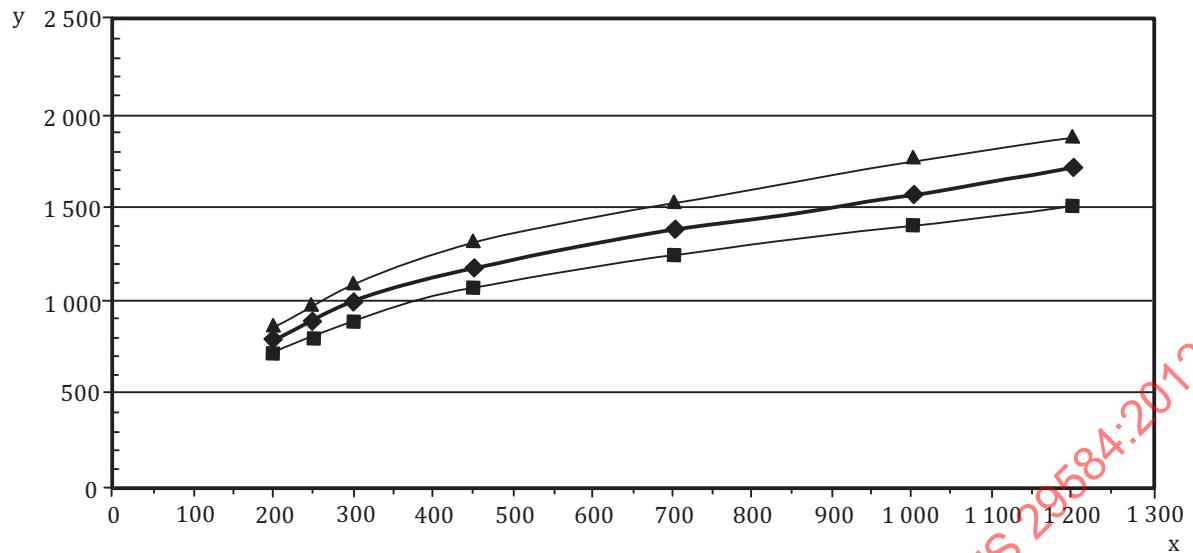**Key**

- ◆ mean value
- mean value minus 10 %
- ▲ mean value plus 10%
- x drop height h
- y mean peak vertical micro-strain for twin tyre impactor ($\varepsilon_{TT,V} \times 10^6$)

Figure B.2 — Reference vertical micro-strain calibration curve for twin tyre impactor**Table B.4 — Reference mean peak horizontal micro-strain for shot bag impactor**

| Drop height mm | Mean value $\varepsilon_{SB,H} \times 10^6$ | Mean value- minus 10 % | Mean value- plus 10 % |
|-------------------|--|---------------------------|-----------------------|
| 200 | 1 174 | 1 057 | 1 291 |
| 250 | 1 298 | 1 169 | 1 428 |
| 300 | 1 434 | 1 290 | 1 577 |
| 450 | 1 762 | 1 586 | 1 939 |
| 700 | 2 159 | 1 943 | 2 375 |
| 1 000 | 2 567 | 2 311 | 2 824 |
| 1 200 | 2 764 | 2 487 | 3 040 |

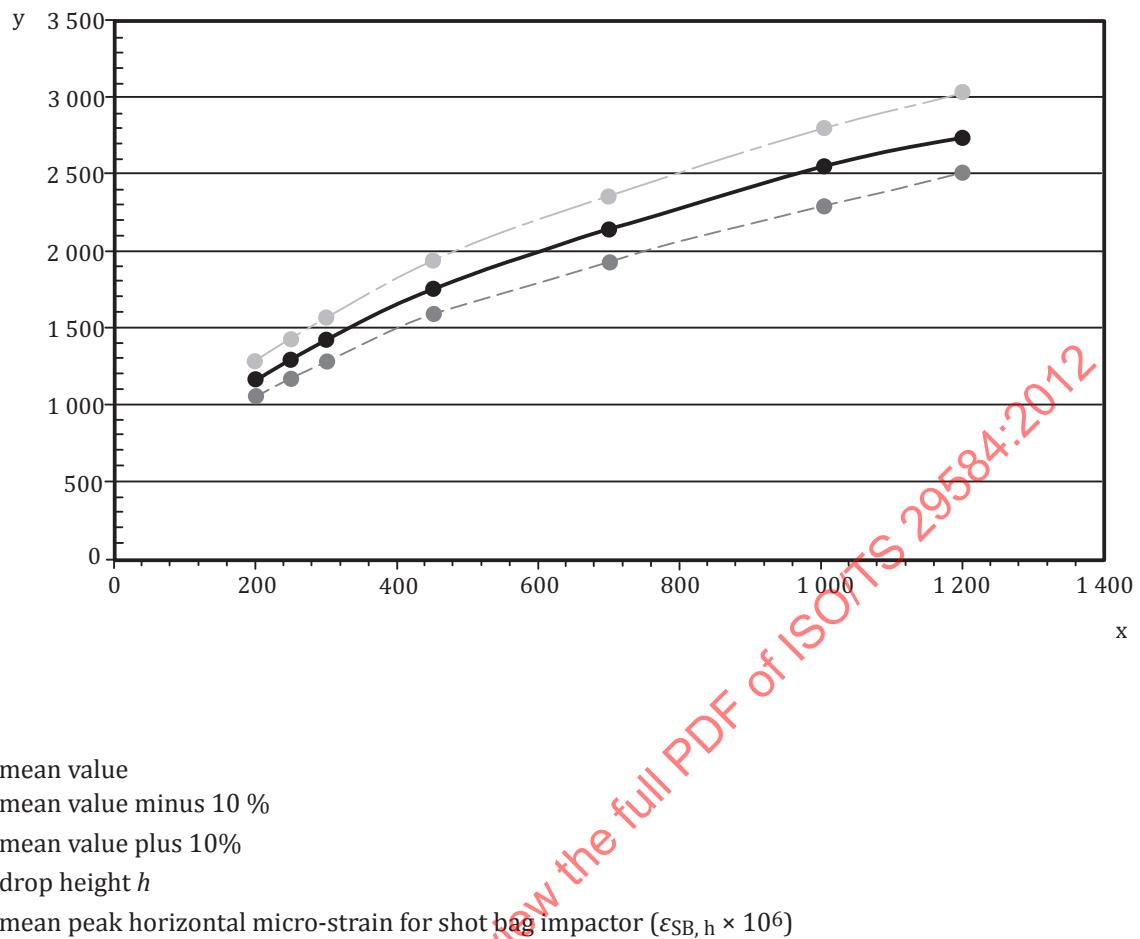
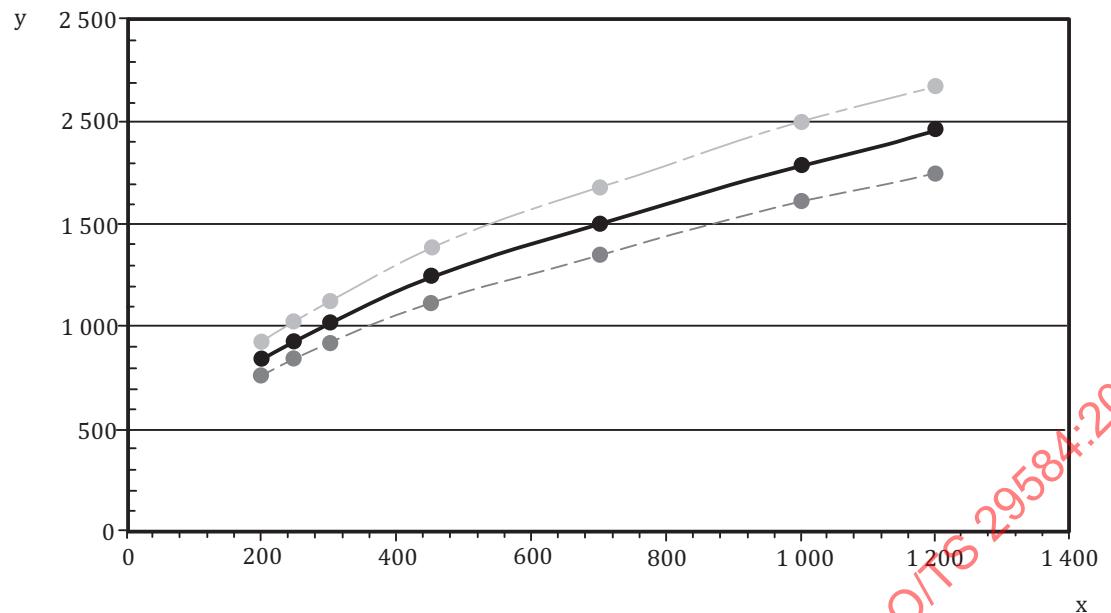


Figure B.3 — Reference horizontal micro-strain calibration curve for shot bag impactor

Table B.5 — Reference mean peak vertical micro-strain for shot bag impactor

| Drop height mm | Mean value $\varepsilon_{SB, v} \times 10^6$ | Mean value- minus 10 % | Mean value- plus 10 % |
|-------------------|---|---------------------------|-----------------------|
| 200 | 843 | 759 | 928 |
| 250 | 943 | 849 | 1 038 |
| 300 | 1 029 | 926 | 1 131 |
| 450 | 1 249 | 1 124 | 1 373 |
| 700 | 1 512 | 1 361 | 1 664 |
| 1 000 | 1 810 | 1 629 | 1 991 |
| 1 200 | 1 963 | 1 767 | 2 160 |

**Key**

- mean value
- mean value minus 10 %
- mean value plus 10%

x drop height h
y mean peak vertical micro-strain for shot bag impactor $(\epsilon_{SSB,v} \times 10^6)$

Figure B.4 — Reference vertical micro-strain calibration curve for shot bag impactor

Annex C (normative)

Sphere penetration test

C.1 Probe assembly

The probe assembly shall consist of a sphere³⁾ of diameter (76 ± 1) mm connected to an arm with a device⁴⁾ for measuring when a maximum force of 25 N has been applied. An example of a probe assembly is shown in Figure C.1.


C.2 Operation

The probe assembly shall be held so that it is horizontal. It shall then be pushed into any opening formed in the test piece. The weakest point of resistance shall be selected. A horizontal force shall be applied until either:

- a) a maximum force of 25 N has been achieved without penetration by the sphere — the test piece shall be deemed to have passed the test;
- b) the maximum diameter of the sphere has passed through the plane of the test piece without a force of 25 N being achieved — the test piece shall be deemed to have failed the test.

3) A sphere available from Euromatic is an example of a suitable product available commercially. This information is given for the convenience of users of this Technical Specification and does not constitute an endorsement by ISO of this product.

4) The portable force indicator, model PF1-200N, is an example of a suitable product available commercially. This information is given for the convenience of users of this Technical Specification and does not constitute an endorsement by ISO of this product.

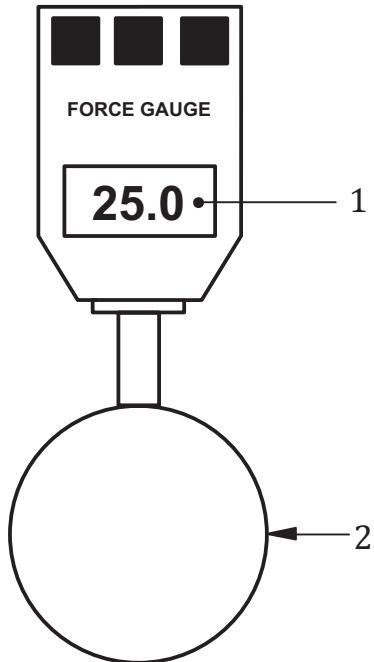

Key

- 1 force indicated in Newtons
- 2 76 mm diameter sphere

Figure C.1 — Example of a probe to verify free passage of a 76 mm diameter sphere

Annex D (informative)

Example of a test rig

See Figures D.1 to D.3.


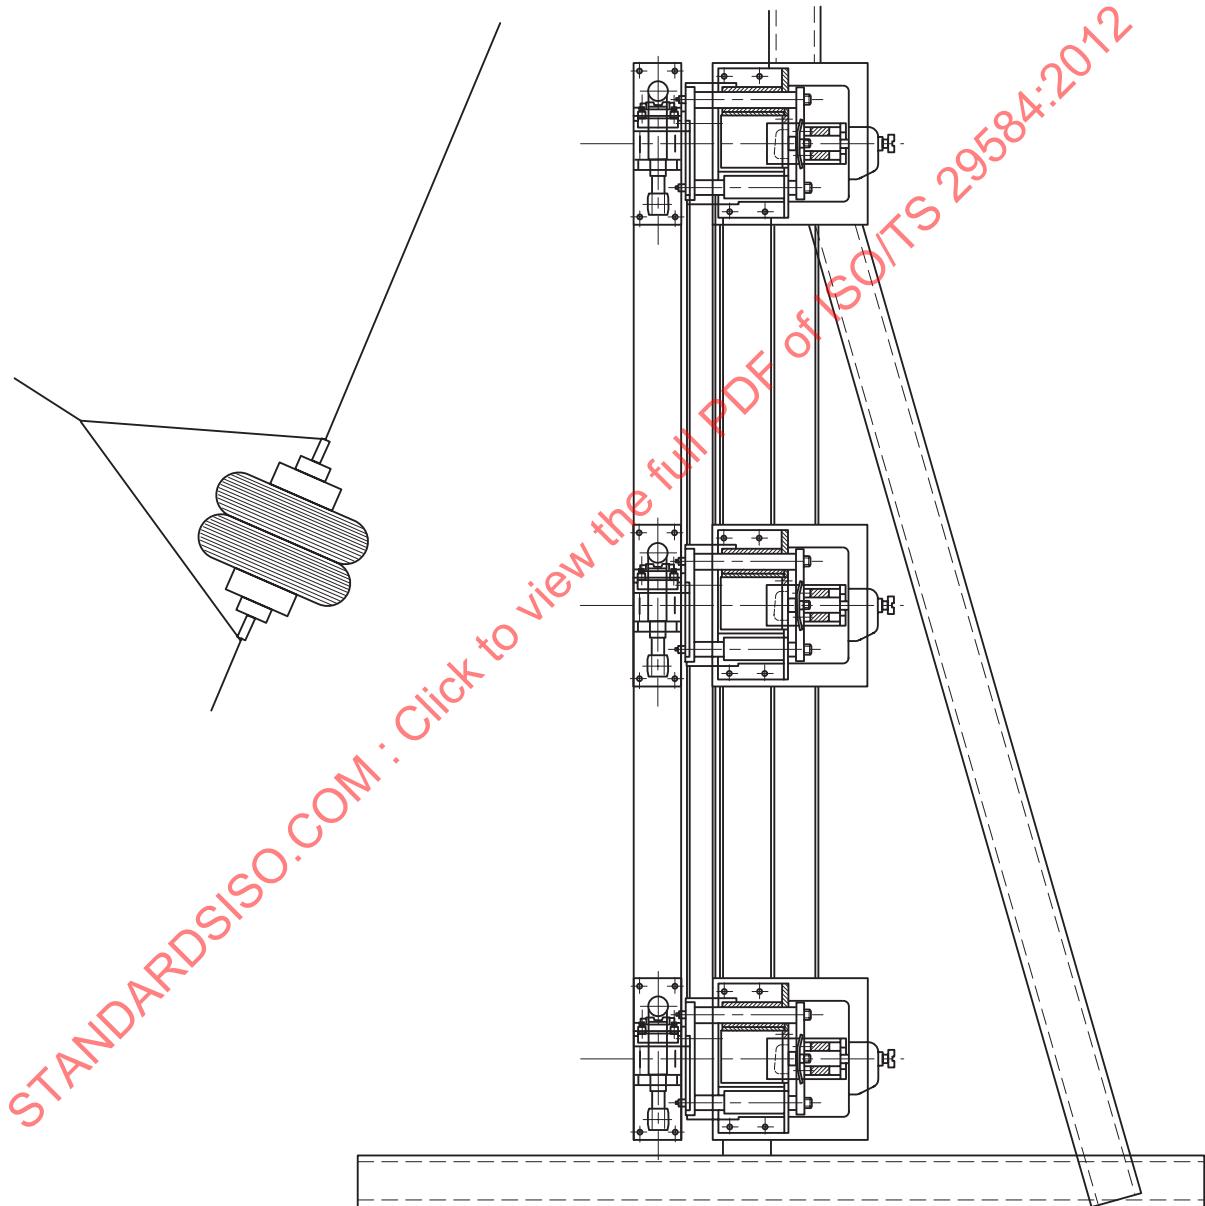


Figure D.1 — Side elevation of the main frame with the impactor

Dimensions in millimetres

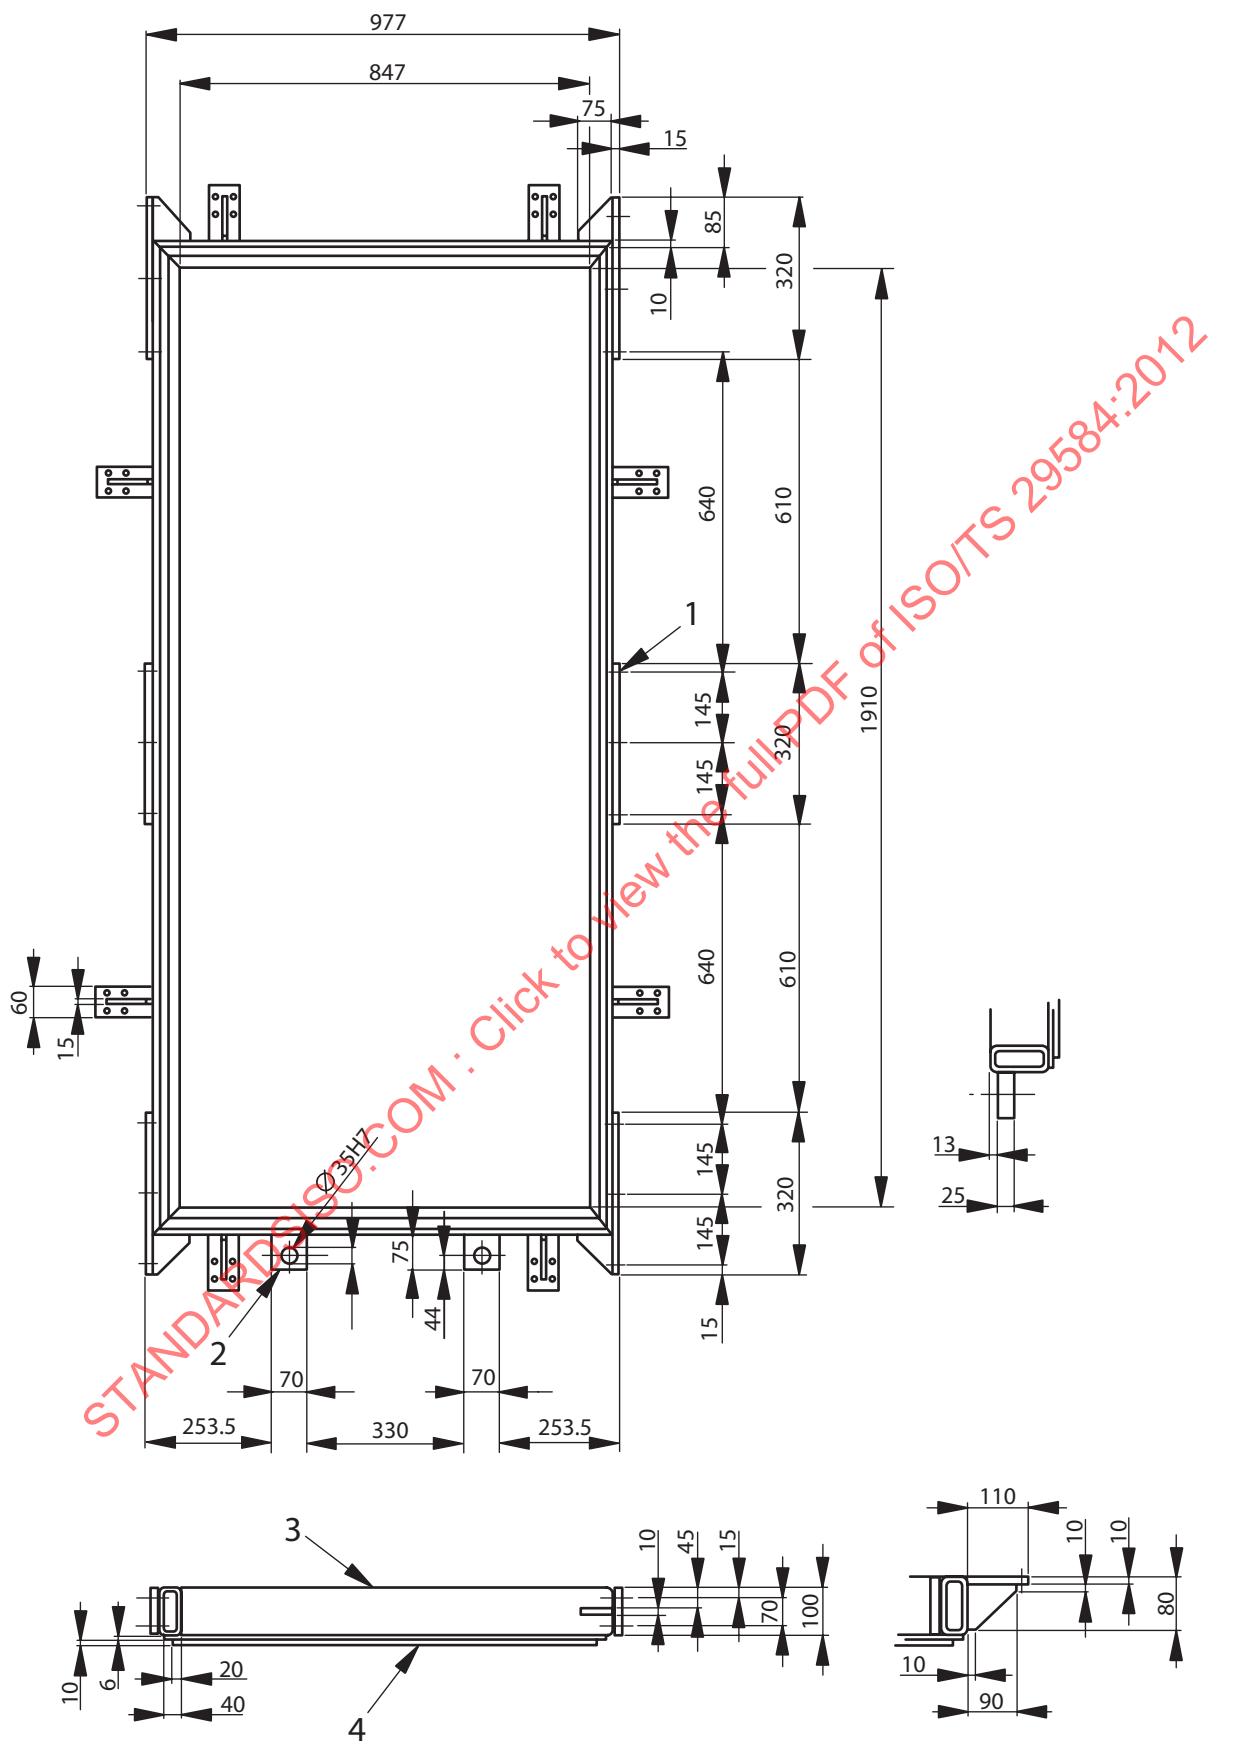

Key


1 12 holes Ø M12
2 see detail

3 100 × 50 × 8 right hand side
4 rubber strips 20 × 10

Figure D.2 — Component No. 1



Dimensions in millimetres

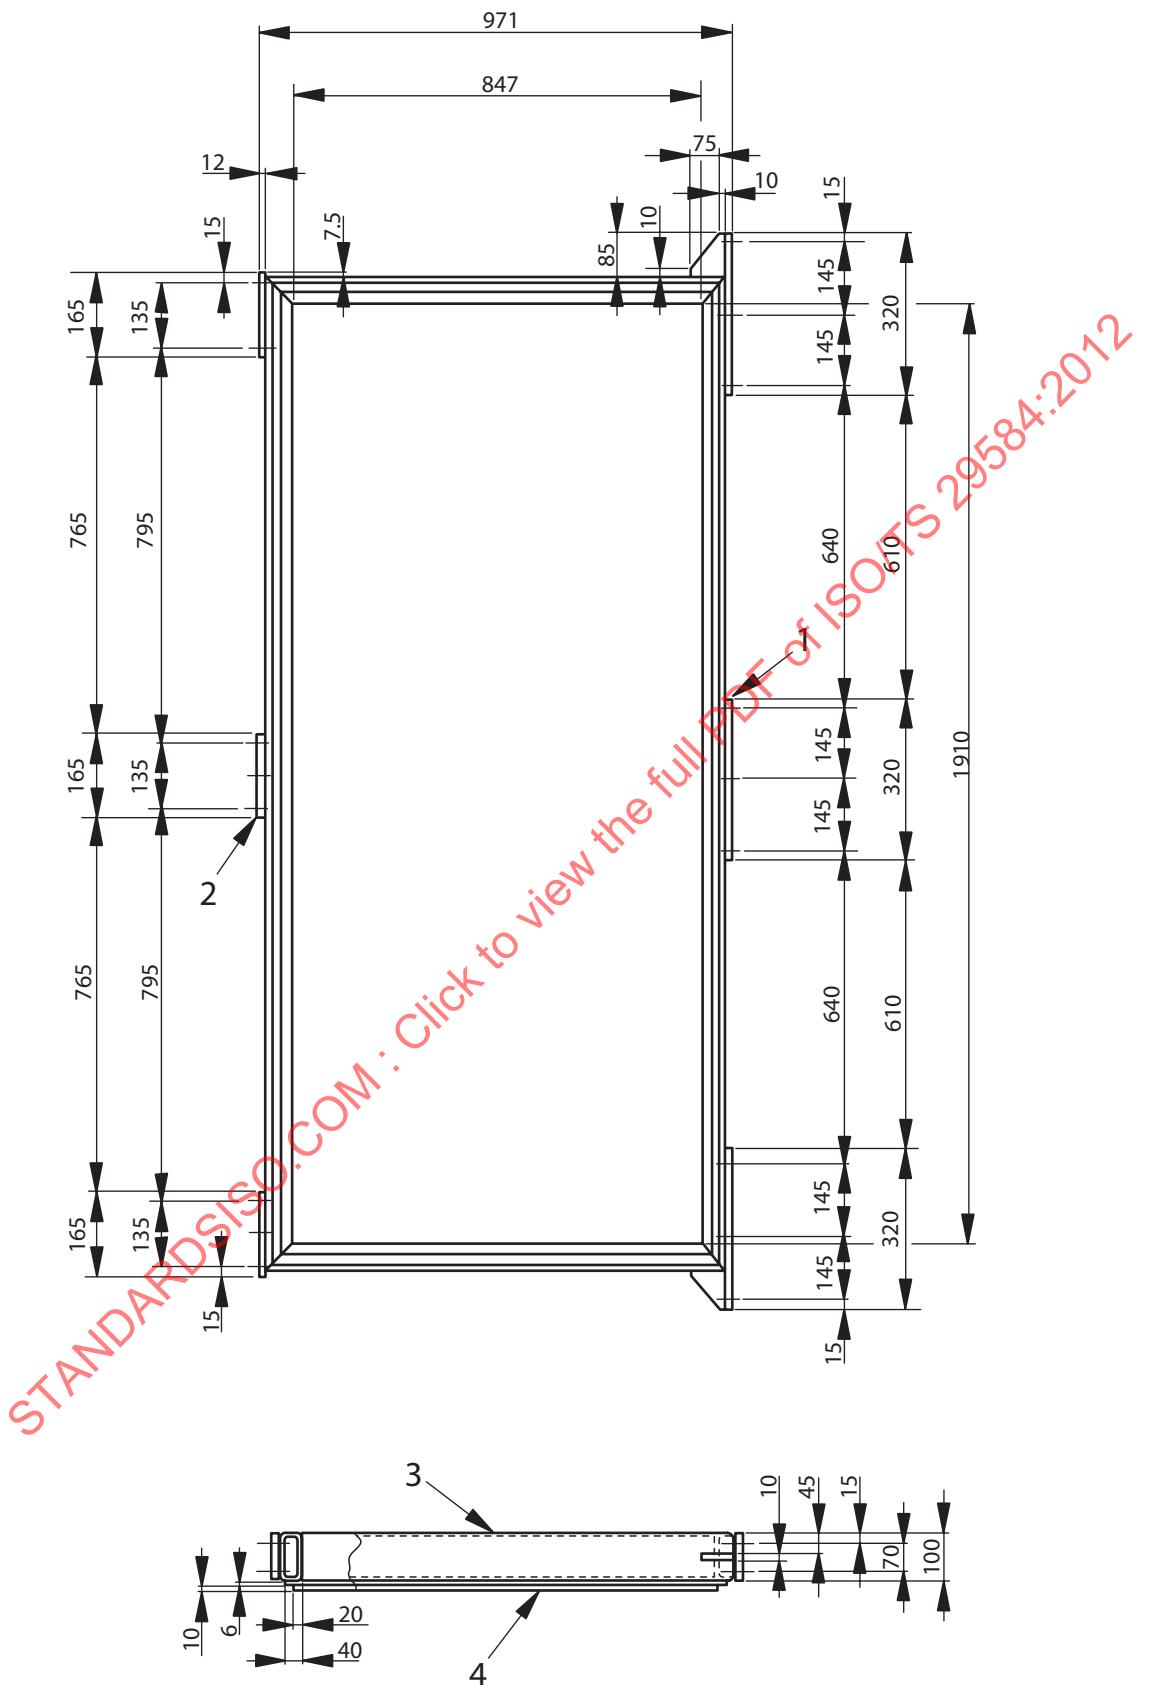**Key**

1 18 holes Ø M12
2 12 holes Ø M12

3 100 × 50 × 8 right hand side
4 rubber strips 20 × 10